

# One-dimensional photonic crystal slot waveguide for silicon-organic hybrid electro-optic modulators

Hai Yan<sup>a</sup>, Xiaochuan Xu<sup>b</sup>, Chi-Jui Chung<sup>a</sup>, Harish Subbaraman<sup>b</sup>, Zeyu Pan<sup>a</sup>, Swapnajit Chakravarty<sup>b</sup>, and Ray T. Chen<sup>a,b,\*</sup>

<sup>a</sup>Department of Electrical and Computer Engineering, The University of Texas at Austin, Austin, TX 78758, USA;

<sup>b</sup>Omega Optics Inc., 8500 Shoal Creek Blvd., Austin, TX, 78759, USA  
\*raychen@uts.cc.utexas.edu

## ABSTRACT

A one-dimensional (1D) photonic crystal (PC) slot waveguide was proposed and experimentally demonstrated for integrated silicon-organic hybrid modulators. The 1D PC slot waveguide consists of a conventional silicon slot waveguide with periodic rectangular teeth on its two rails. This structure takes advantage of large mode overlap in a conventional slot waveguide and the slow light enhancement from the PC structure. Its simple geometry makes it resistant to fabrication imperfections and helps reduce the propagation loss. The observed effective EO coefficient in an actual Mach-Zehnder interferometer modulator is as high as 490 pm/V owing to slow light effect.

**Keywords:** photonic crystal waveguides, slow light, electro-optic modulators, silicon-organic hybrid devices, slot waveguides, electro-optic polymer devices

## 1. INTRODUCTION

The network interconnects, including conventional data networks and inter/intra chip data links, has seen a gradual transition from electrical to optical technology<sup>1</sup>. Optical interconnect is trending to short distances rapidly with its unique advantages of ultra-high bandwidth and chip-scale integration capability on silicon substrate. Among the optical components for on-chip optical interconnect, electro-optic (EO) modulator is one of the most important. Most silicon integrated EO modulators rely on the plasma dispersion effect, in which the change of free carrier concentration induces the change of refractive index in silicon waveguide<sup>2,3</sup>. The bandwidths and modulation efficiencies of these modulators are therefore limited by the free carrier dynamics. On the other hand, polymer EO materials possess intriguing second-order nonlinear optical property, such as high nonlinear coefficient and ultrafast response time, and can be applied easily through spin-casting<sup>4-6</sup>. The silicon-organic hybrid platform combines advantages of both silicon photonic and polymer materials, thus is a promising candidate for high-performance EO modulation applications<sup>7-9</sup>.

Silicon-organic hybrid EO modulators based on various phase shifter designs have been reported in recent years. These structures include slot waveguide<sup>10-13</sup>, two-dimensional (2D) slot photonic crystal (PC) waveguide<sup>14-16</sup> and one-dimensional (1D) PC waveguide<sup>17</sup>. High modulation efficiency has been achieved in slot waveguides because of the strong confinement of optical mode in low index slot region infiltrated with EO materials, which leads to large mode volume overlap with EO polymer. Slow light waveguides, like 2D slot PC waveguides, have also been proposed, which utilize the slow light effect and greatly enhance effective  $r_{33}$ . In 2D slot PC waveguide, however, the optical loss in slow light region and its robustness to fabrication variations is a concern, especially in a dispersion-engineered PC slot waveguide considering its complicated structure and delicate arrangement of the PC holes. Reports have shown that the propagation loss in a 2D PC slot is very sensitive to slot width variations<sup>18</sup>. In [17], a novel 1D PC structure is introduced. With proper use of the air band in the PC, the structure achieves high mode overlap ( $\sigma = 0.67$ ) and slow light enhancement simultaneously, although the poling efficiency of the EO polymer between the pillars is relatively low because voltage drop in this area is reduced by the silicon pillars.

In reality, the mode overlap with EO material, effective  $r_{33}$  (proportional to slow light enhancement), and propagation loss are among the most important factors for a silicon-organic hybrid EO modulator, yet there is a lack of comprehensive consideration on all these factors. Here we propose a new slow light slot waveguide with 1D PC structure which takes all these factors into consideration. We further define a comprehensive figure-of-merit to compare

it with previous reported modulator phase shifter designs. The proposed 1D PC structure takes advantage of the strong mode confinement in the low-index region of a conventional slot waveguide together with the slow light enhancement from the 1D PC. Its simple geometry makes it robust to fabrication imperfections and helps reduce the propagation loss, while still maintaining the benefit of large mode overlap and slow light enhancement. Using it as a phase shifter and converting the phase shift to amplitude modulation through a Mach-Zehnder interferometer (MZI) structure, we demonstrate an integrated silicon-organic hybrid EO modulator. The observed effective EO coefficient is as high as 490 pm/V around 1550 nm. The measured half wave voltage and length product is 0.91 V·cm and can be further improved. The proposed structure offers a competitive novel phase shifter design, which is compact, simple, highly efficient and with low optical loss, for on-chip silicon-organic hybrid EO modulators.

## 2. DEVICE DESIGN AND FABRICATION

The structure of the 1D PC slot waveguide is shown in Fig. 1. It is formed by a conventional slot waveguide with periodic rectangular teeth on its rails. The structural parameters of the 1D PC slot are chosen to support single mode propagation while achieving high group index (slow light) around the optical wavelength of 1550 nm. The period ( $P$ ) of the rectangular teeth is 415 nm. The width ( $a$ ) and length ( $b$ ) of the teeth are 124.5 nm ( $0.3P$ ) and 300 nm, respectively. The slot has a width ( $S_w$ ) of 150 nm and a rail width ( $R_w$ ) of 100 nm. The 1D PC slot waveguide sits on top of a silicon dioxide layer and is covered with EO polymer (SEO 125 Soluxra, LLC.,  $n=1.63$ ). Fig. 2(a) shows the simulated photonic band diagram of the quasi-transverse-electric (TE) modes of the 1D PC slot waveguide using 3D plane wave expansion method. The nearly flat region of the lowest band is chosen as the operating range. It supports propagation mode in the PC slot waveguide and has a high group index ( $n_g > 40$ ) close to the band edge. The electric field intensity distribution of the mode at the band edge is shown in Fig. 2(b) and (c). Optical power is strongly confined in the slot and the ratio of the optical power in the EO polymer region is calculated to be  $\sigma = 0.35$ .

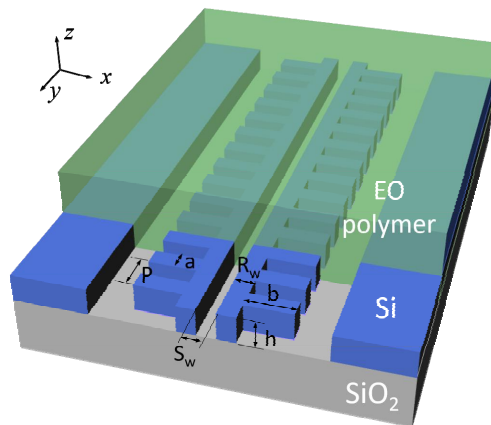


Figure 1. Schematic of the proposed 1D PC slot waveguide filled with EO polymer as a phase shifter for EO modulators.

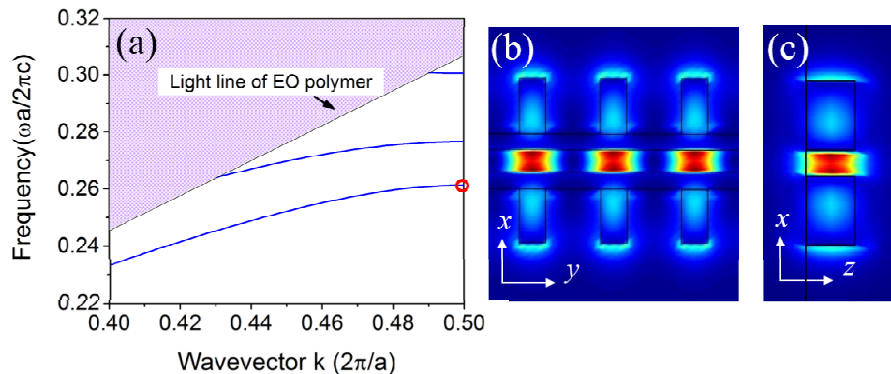


Figure 2. Schematic of the proposed 1D PC slot waveguide filled with EO polymer as a phase shifter for EO modulators.

The 1D PC slot waveguide is accessed through conventional slot waveguides. To compensate the mode mismatch and improve coupling efficiency at the interface of the conventional slot waveguide and the 1D PC slot waveguide, a coupler is designed. Instead of using adiabatically tapered long coupler<sup>19</sup>, a very short intermediate low-group-index coupler (step taper) is used<sup>20</sup>. The schematic of the step taper is shown in Fig. 3(a). The optimized step taper consists of 5 periods of PC slot waveguide with shorter teeth ( $b_T = 200\text{nm}$ ) and slightly larger period ( $P_T = 425\text{nm}$ ). The width of the teeth remains unchanged ( $a_T = 0.3P_T$ ,  $127.5\text{nm}$ ). The parameters of the step taper (period  $P_T$ , tooth length  $b_T$  and width  $a_T$ , number of periods  $N$ ) were optimized by transmission spectrum simulation using 3D finite difference time domain (FDTD) method. Fig. 3(b) compares the simulated transmission before and after implementing the optimized step taper. It can be seen from the figure that the large fluctuations resulting from the group index mismatch has been significantly reduced by the short step taper (total length  $\sim 2\ \mu\text{m}$ ) and the additional loss caused by the taper is negligible. Fig. 3(c) shows the measured transmission spectrum of a  $200\ \mu\text{m}$  long 1D PC slot waveguide filled with EO polymer. A clear band edge can be observed near  $1550\ \text{nm}$ .

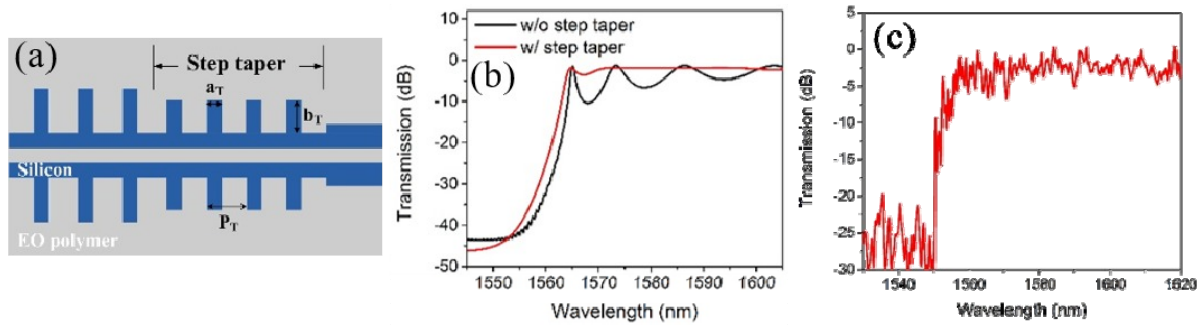


Figure 3. (a) Schematic of the step taper; (b) Simulated transmission spectrum comparing 1D PC slot waveguide with (red curve) and without step taper (black curve); (c) Measured transmission spectrum of 1D PC slot waveguide with optimized step taper.

To characterize the 1D PC slot waveguide as the phase shifter for modulators, an MZI structure was designed with one arm loaded with a  $200\ \mu\text{m}$  long 1D PC slot waveguide, as illustrated in Fig. 4(a). The proposed 1D PC slot waveguide, along with all connecting strip waveguides, 1 by 2 multi-mode interferometer (MMI), and subwavelength grating couplers, were patterned by e-beam lithography on a silicon-on-insulator (SOI) chip with  $250\ \text{nm}$  thick top silicon layer. The pattern was then transferred onto the silicon layer through a single reactive ion etching (RIE) step. Gold electrodes were formed by photolithography, e-beam evaporation, and lift-off process. The gap size between the two electrodes is  $4\ \mu\text{m}$ . Fig. 4(b) show the scanning electron microscope (SEM) images of the fabricated silicon PC slot waveguide, strip-to-slot mode converter and grating coupler and also the microscopic image of the MMI up to the above steps. Finally, EO polymer was coated on the PC slot waveguide and cured overnight under vacuum at  $80\ ^\circ\text{C}$ . It ensures that the polymer infiltrates the PC slot structures thoroughly. Before modulation measurement, the EO polymer goes through a poling process at its glass transition temperature of  $150\ ^\circ\text{C}$  with an external electric field of  $100\ \text{V}/\mu\text{m}$  applied through the gold electrodes. The poling process aligns the chromophores in the same direction in the host polymer and activate its EO effect.

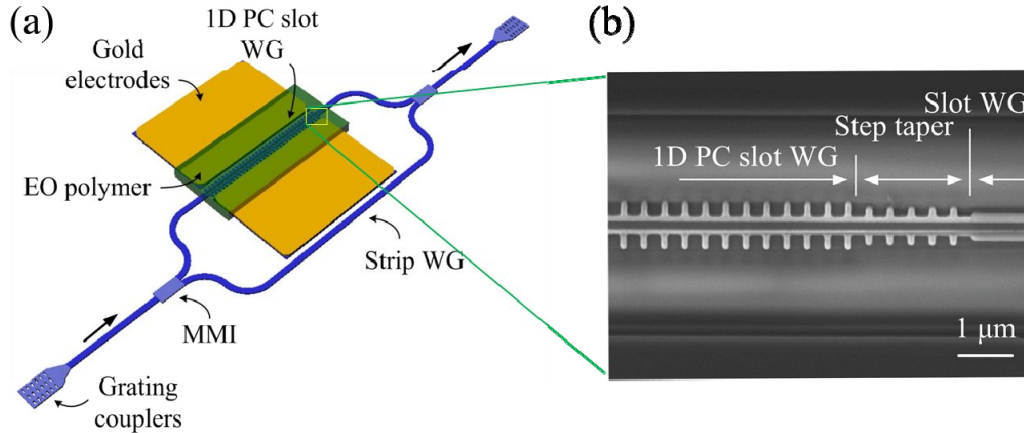


Figure 4. (a) Schematic of a MZI modulator based on 1D PC slot waveguide; (b) scanning electron microscope (SEM) images of the 1D PC slot waveguide and step taper.

### 3. RESULTS AND DISCUSSION

Transmission spectra of the fabricated device were obtained from a testing platform using a broadband amplified spontaneous emission (ASE) source (1510nm-1630nm) and an optical spectrum analyzer. Light from the ASE source was guided through a polarizer to subwavelength grating couplers and excites the fundamental quasi-TE mode of the on-chip strip waveguides. Transmission spectrum of the unbalanced MZI without applying any voltage on the electrodes was first measured and shown in Fig. 5(a). The oscillations in the spectra are due to the group velocity difference between the two arms of the MZI. The oscillation period decreases rapidly at the band edge of the 1D PC slot waveguide, approximately 1567nm. The group index therefore can be estimated from the oscillation patterns using the equation:  $n_g^{pcw}(\lambda) = n_g^{ref}(\lambda) + \lambda_{min} \lambda_{max} / (2L(\lambda_{min} - \lambda_{max}))$ , where  $n_g^{pcw}$  is the group index of the 1D PC slot waveguide,  $n_g^{ref}$  is the group index of the reference strip waveguide ( $n_g^{ref} = 4.2$ ),  $\lambda_{min}$  and  $\lambda_{max}$  are the wavelength at adjacent valley and peak of the oscillations,  $L = 200 \mu\text{m}$  is the length of the phase shifter. The estimated group indices are drawn in the same plot. Group index over 25 is observed. The slow light region has a width of about 1.5nm (marked with color) with an average group index around 20 and can be improved by dispersion engineering<sup>15</sup>. The total loss of the MZI structure is ~10dB, which includes propagation loss of the 200  $\mu\text{m}$  1D PC slot waveguide (~3dB), coupling loss on the step taper (~3dB), mode converter (~2dB), and MMI (~2dB). The propagation loss in the 1D PC slot is estimated at about 15dB/mm. This loss is higher than conventional slot waveguide filled with EO polymer (4dB/mm)<sup>10</sup> due to scattering at the periodic structure but is smaller than the 2D PC slot waveguide under similar fabrication conditions. The much simpler structure of 1D periodic teeth along the slot waveguide reduces the scattering loss, which is a major source of loss in real devices, and make the device more robust against fabrication imperfections.

To characterize the device performance, electric field was applied on the phase shifter through the electrodes. Fig. 5(b) shows the transmission spectra under different electric fields generated by DC voltage. The spectra show red shifts with increasing electric field from 0 to 10 V/ $\mu\text{m}$ . The phase shift induced by the applied electric field can be estimated from the equation  $\Delta\phi = 2\pi\Delta\lambda / FSR$ , where FSR is the free spectral range of the oscillations in the MZI spectrum. The half-wave voltage, which is the applied voltage when  $\Delta\phi = \pi$ , is estimated according to the relationship between applied voltage and wavelength shift obtained from the spectra. Based on these equations, EO modulation efficiency ( $V_\pi L$ ) of 0.91 V·cm is calculated near the wavelength of 1562 nm. The effective EO coefficient of the EO polymer,  $r_{33eff}$ , can then be estimated by<sup>14</sup>:  $r_{33eff} = \lambda W / n^3 V_\pi \sigma L$ , where  $n = 1.63$  is the refractive index of the EO polymer,  $\sigma$  is the ratio of optical mode power in the EO polymer,  $W$  is the gap size between the electrodes. The estimated  $r_{33eff}$  near 1562 nm is 490 pm/V. This high  $r_{33}$  value is a result of the enhancement effect of slow group velocity of the waveguide mode. Fig. 5(c) shows the group index and effective EO coefficient as a function of wavelength in the same diagram. The increasing

$r_{33\text{eff}}$  with increasing group index confirms that the effective EO coefficients and thus modulation efficiencies are enhanced by the slow light effect in our proposed PC slot waveguide.

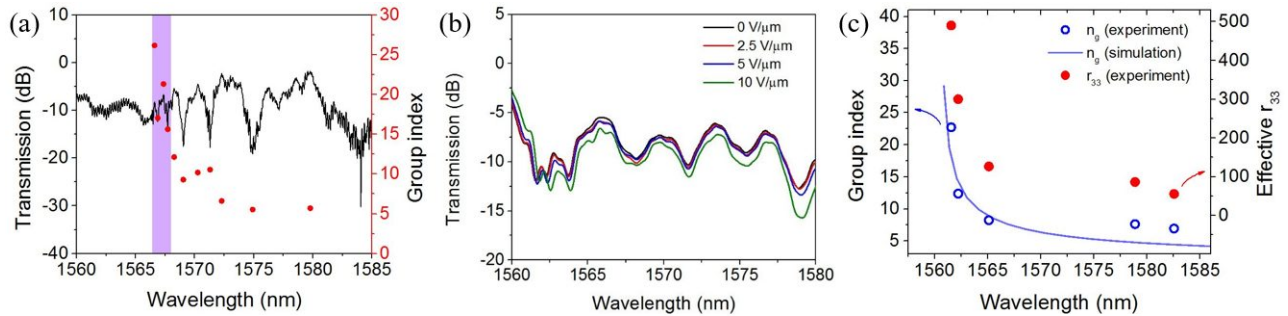


Figure 5. (a) Measured transmission spectrum of the MZI structure and derived group index as a function of wavelength; (b) Measured transmission spectra of the MZI modulator with different DC electric field applied on the electrodes; (c) Group index (from both simulation and experiment) and effective  $r_{33}$  as a function of wavelength.

In order to study the potential of phase shifter designs comprehensively, we define a figure-of-merit  $f = \sigma \cdot n_g \cdot L_{3dB}$ , where  $\sigma$  is the ratio of optical mode in the EO polymer region,  $n_g$  is group index in the waveguide,  $L_{3dB}$  is the length of phase shifter in  $mm$  with 3dB propagation loss. This figure-of-merit reflects a phase shifter's ability to efficiently confine and modulate the propagation mode in the waveguide. In our proposed 1D PC slot structure,  $f = 0.35 \times 20 \times 0.2 \sim 1.4$  considering the 15dB/mm propagation loss. In conventional slot waveguide based EO modulators, like the ones in [10,11,13],  $f \sim 0.4 \times 2 \times 0.75 \sim 0.6$  considering typical propagation loss of 4dB/mm when filled with EO polymer<sup>10</sup>. In a 2D PC slot waveguide<sup>14,16</sup>,  $\sigma$  and  $n_g$  are similar to our proposed 1D PC waveguide, but the  $L_{3dB}$  is smaller due to the larger scattering loss from the 2D PC structure. It can be seen that in 1D PC slot waveguide, the slow light effect provides more benefits than the extra propagation loss it induces, while the overlap factor is as high as that in conventional slot waveguides. Therefore, the proposed 1D PC slot waveguide has the potential to enable better efficiency in EO modulators comparing to those based on conventional slot waveguides or 2D PC slot waveguides.

The above measurement results demonstrate the slow light enhancement in the proposed structure. However, this modulator is not optimized for low voltage, high extinction ratio and high speed operation. To further reduce the half-wave voltage, it is feasible to use strip-loaded structure<sup>12</sup> or add narrow contacting arms to the PC teeth and connect the bulk silicon under the electrodes<sup>11</sup>. A push-pull configuration will help both lower the operating voltage and improve the extinction ratio. Considering high speed operation, the silicon slabs between the electrodes and the slot filled with EO polymer is similar to a RC circuit, where the 3dB frequency bandwidth can be estimated by  $1/2\pi RC$ . Through finite element simulation, the 3-dB bandwidth is about 61 GHz ( $R=6.9k\Omega$ ,  $C=0.38fF$ ). To make the most out of the ultra-fast response time of EO polymer material, the silicon slab can be properly doped to further reduce the equivalent resistance and improve the bandwidth<sup>10,15</sup>. With these additional considerations, the silicon-organic hybrid modulator has the potential of high speed operation of tens of Gbit/s or even higher<sup>7,10,21</sup>.

#### 4. SUMMARY

In summary, we have designed a slow light slot waveguide that has a 1D PC structure and demonstrated its enhancement effect in an MZI EO modulator. Its simple geometry makes it more robust to fabrication imperfections and helps reduce the propagation loss, but still maintain the benefit of a slow light waveguide. The effective EO coefficient raises to 490 pm/V due to slow light enhancement. The observed half wave voltage and length product is less than 1 V·cm and can be further improved with further electrical design. This proposed structure provides a new platform for applications that require maximum light-matter interaction within a short length, especially for silicon-organic hybrid EO modulators in on-chip optical interconnect.

#### ACKNOWLEDGMENT

The authors would like to acknowledge the support by Air Force Research Laboratory (AFRL) Small Business Technology Transfer Research (STTR) program (FA8650-14-C-5006).

## REFERENCES

- [1] Reed, G., Mashanovich, G., Gardes, F., Thomson, D., "Silicon optical modulators," *Nat. Photonics* **4**(8), 518–526, Nature Publishing Group (2010).
- [2] Liao, L., Samara-Rubio, D., Morse, M., Liu, A., Hodge, D., Rubin, D., Keil, U. D., Franck, T., "High speed silicon Mach-Zehnder modulator," *Opt. Express* **13**(8), 3129 (2005).
- [3] Green, W. M., Rooks, M. J., Sekaric, L., Vlasov, Y. a., "Ultra-compact, low RF power, 10 Gb/s silicon Mach-Zehnder modulator," *Opt. Express* **15**(25), 17106 (2007).
- [4] Bortnik, B., Hung, Y.-C., Tazawa, H., Seo, B.-J., Luo, J., Jen, A. K.-Y., Steier, W. H., Fetterman, H. R., "Electrooptic Polymer Ring Resonator Modulation up to 165 GHz," *IEEE J. Sel. Top. Quantum Electron.* **13**(1), 104–110 (2007).
- [5] Enami, Y., Derosé, C. T., Mathine, D., Loychik, C., Greenlee, C., Norwood, R. A., Kim, T. D., Luo, J., Tian, Y., et al., "Hybrid polymer/sol-gel waveguide modulators with exceptionally large electro-optic coefficients," *Nat. Photonics* **1**(3), 180–185 (2007).
- [6] Lee, M., "Broadband Modulation of Light by Using an Electro-Optic Polymer," *Science* (80-. ). **298**(5597), 1401–1403 (2002).
- [7] Leuthold, J., Freude, W., Brosi, J., Baets, R., Dumon, P., Biaggio, I., Scimeca, M. L., Diederich, F., Frank, B., et al., "Silicon Organic Hybrid Technology&#x2014;A Platform for Practical Nonlinear Optics," *Proc. IEEE* **97**(7), 1304–1316 (2009).
- [8] Qiu, F., Spring, A. M., Maeda, D., Ozawa, M., Odoi, K., Otomo, A., Aoki, I., Yokoyama, S., "A hybrid electro-optic polymer and TiO<sub>2</sub> double-slot waveguide modulator," *Sci. Rep.* **5**, 8561, Nature Publishing Group (2015).
- [9] Haffner, C., Heni, W., Fedoryshyn, Y., Niegemann, J., Melikyan, a., Elder, D. L., Baeuerle, B., Salamin, Y., Josten, a., et al., "All-plasmonic Mach-Zehnder modulator enabling optical high-speed communication at the microscale," *Nat. Photonics* **9**(8), 525–528 (2015).
- [10] Palmer, R., Koeber, S., Elder, D. L., Woessner, M., Heni, W., Korn, D., Lauermann, M., Bogaerts, W., Dalton, L., et al., "High-speed, low drive-voltage silicon-organic hybrid modulator based on a binary-chromophore electro-optic material," *J. Light. Technol.* **32**(16), 2726–2734 (2014).
- [11] Baehr-Jones, T., Penkov, B., Huang, J., Sullivan, P., Davies, J., Takayesu, J., Luo, J., Kim, T. D., Dalton, L., et al., "Nonlinear polymer-clad silicon slot waveguide modulator with a half wave voltage of 0.25 v," *Appl. Phys. Lett.* **92**(16), 1–4 (2008).
- [12] Ding, R., Baehr-Jones, T., Liu, Y., Bojko, R., Witzens, J., Huang, S., Luo, J., Benight, S., Sullivan, P., et al., "Demonstration of a low V<sub>π</sub>L modulator with GHz bandwidth based on electro-optic polymer-clad silicon slot waveguides," *Opt. Express* **18**(15), 15618, OSA (2010).
- [13] Palmer, R., Alloatti, L., Korn, D., Schindler, P. C., Schmogrow, R., Heni, W., Koenig, S., Bolten, J., Wahlbrink, T., et al., "Silicon-Organic Hybrid MZI Modulator Generating OOK, BPSK and 8-ASK Signals for Up to 84 Gbit/s," *IEEE Photonics J.* **5**(2), 6600907–6600907 (2013).
- [14] Wang, X., Lin, C.-Y., Chakravarty, S., Luo, J., Jen, A. K.-Y., Chen, R. T., "Effective in-device r<sub>33</sub> of 735 pm/V on electro-optic polymer infiltrated silicon photonic crystal slot waveguides," *Opt. Lett.* **36**(6), 882, Optical Society of America (2011).
- [15] Zhang, X., Hosseini, A., Chakravarty, S., Luo, J., Jen, A. K.-Y., Chen, R. T., "Wide optical spectrum range, subvolt, compact modulator based on an electro-optic polymer refilled silicon slot photonic crystal waveguide," *Opt. Lett.* **38**(22), 4931 (2013).
- [16] Lin, C. Y., Wang, X., Chakravarty, S., Lee, B. S., Lai, W., Luo, J., Jen, A. K. Y., Chen, R. T., "Electro-optic polymer infiltrated silicon photonic crystal slot waveguide modulator with 23 dB slow light enhancement," *Appl. Phys. Lett.* **97**(9), 2013–2016 (2010).
- [17] Inoue, S., Otomo, A., "Electro-optic polymer/silicon hybrid slow light modulator based on one-dimensional photonic crystal waveguides," *Appl. Phys. Lett.* **103**(17), 171101 (2013).
- [18] Di Falco, A., Massari, M., Scullion, M. G., Schulz, S. A., Romanato, F., Krauss, T. F., "Propagation Losses of Slotted Photonic Crystal Waveguides," *IEEE Photonics J.* **4**(5), 1536–1541 (2012).
- [19] Lin, C.-Y., Wang, A. X., Lai, W.-C., Covey, J. L., Chakravarty, S., Chen, R. T., "Coupling loss minimization of slow light slotted photonic crystal waveguides using mode matching with continuous group index perturbation," *Opt. Lett.* **37**(2), 232 (2012).
- [20] Hosseini, A., Xu, X., Kwong, D. N., Subbaraman, H., Jiang, W., Chen, R. T., "On the role of evanescent modes and group index tapering in slow light photonic crystal waveguide coupling efficiency," *Appl. Phys. Lett.* **98**(3), 3–5 (2011).

- [21] Hochberg, M., Baehr-Jones, T., Wang, G., Shearn, M., Harvard, K., Luo, J., Chen, B., Shi, Z., Lawson, R., et al., "Terahertz all-optical modulation in a silicon-polymer hybrid system," *Nat. Mater.* **5**(9), 703–709 (2006).